



THE EFFECT OF GLUCOSE ON THE HYDRATION KINETICS OF ORDINARY PORTLAND CEMENT

G.C.H. Doudart de la Grée^{1*}, Q.L. Yu¹, H.J.H. Brouwers¹

¹ Eindhoven University of Technology, Department of the Built Environment, P.O. Box 513, 5600 MB, Eindhoven, The Netherlands

*Corresponding author; e-mail: g.c.h.doudart.de.la.gree@tue.nl

Abstract

In this study, the application of fresh-wood-wool without any pre-treatment to produce wood-wool cement boards (WWCB) is investigated. The aim of this study is to create a binder which is less affected by the inhibitory substances of the wood-wool, without reducing the flexural strength properties of the boards. Moreover, the carbon footprint of WWCB is addressed by not using any waterglass and partly replace cement with limestone powder in the boards production. First, the hydration behavior of different binders is studied by means of an isothermal calorimeter, including e.g. different types of cement, addition of glucose as a retarder, reduction of anhydrite in OPC and the use of limestone powder as a partial cement replacement. Then, boards are produced with fresh wood-wool and a newly developed binder recipe that is resulted from the hydration behavior analysis. The results show that the retarding effect of glucose is highly dependent on the chemical composition of the cement. In general, high amounts of C_3A and C_3S in a binder are favorable. When available, glucose reacts first with C_3A , hence, less glucose is available to retard the other cement compounds like C_3S . In addition, when using the fresh wood-wool in boards, the strength of the produced boards is increased. Furthermore, the water absorption of the wood is significantly reduced (20%), since it is already physically and chemically bond within the wood-wool. This enables a lower water demand that results in a denser packing of the binder and a reduced ion migration, leading to a mechanical strength increase. Furthermore, without the use of waterglass and the incorporation of (36%) limestone powder as a partial cement replacement, the CO_2 footprint of the developed board fulfills the stated requirements, while possessing a reduced CO_2 footprint.

Keywords:

WWCB; Hydration kinetics, OPC, Glucose, carbon footprint

1 INTRODUCTION

Wood-wool cement board (WWCB), illustrated in Fig. 1, is a wood-cement composite, made from the reinforcing agent wood-wool, Ordinary Portland Cement (OPC) as binder, water as the reactant and small amounts of additives to catalyze the reaction. The wood-wool is coated with cement and pressed into boards that have densities in the range of 400-650 kg/m^3 with properties that fulfill the requirements stated in the EN 13168.

To meet the aesthetic requirements, wood-wool cement board (WWCB) are produced using different cement types varying between white (CEM I 52.5 R white and grey (CEM I 52.5 R) cement. In case of white cement, they can be painted to any desired color based on their aesthetic requirement. Although the chemical composition and created reaction products of these type of binder defer, it is often neglected. Studies performed on wood-cement composites focus more on the inhibitory influence of soluble compounds of the

wood-wool on the cement hydration which often is linked to the type of wood (Karade, 2010; Fan et al., 2012; Ashori et al., 2011).

However, as stated by Neville, (2002), the content of C_3A which completely reacts with gypsum does not react with a retarder. Hence, the hydration of the calcium silicates is more retarded, which occurs through the adsorption of retarder onto the calcium nuclei. As described by Hachmi and Moslemi, (1990), wood-cement compatibility generally decreases with the increase of the wood extractive, which are generally composed of terpenes, fatty acids, tannins, carbohydrates and inorganic materials (Ashori et al., 2011; Poletto et al., 2012). It is known that sugars contained in wood extractives are responsible for the inhibition of cement setting because they prevent the formation of C-S-H gel and the retarding effect is based on the mechanisms of either adsorption or precipitation (Thomas, 1983).

Currently, three methods are used to overcome the inhibitory effect of wood on cement: (a), by seasoning

the wood logs e.g. storing them outside for approximately 6 months (Aro, 2004); (b), by water treatment e.g. soaking the wood-wool in a water basin with an increased pH (e.g. by calcium hydroxide or cement) in order to accelerate the dissolution of sugars; (c), by the use of accelerators like chlorides (Fan et al., 2012; Pereira et al., 2006; Hachmi et al., 1990; Simatupang & Geimer, 1990). These accelerators are in practice prohibited due to the WWCB is sometimes applied next to the reinforced concrete where the chloride migration from the boards causes the corrosion of the reinforced concrete.

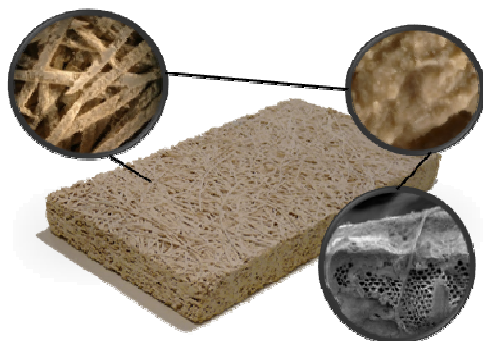


Fig. 1: WWCB created of wood-wool which is mineralized by a white cement creating a protective layer around the wood-wool fiber.

The aim of this study is to create a binder which is less affected by the inhibitory substances of the wood-wool, without reducing the flexural strength properties of the boards. Moreover, the carbon footprint of WWCB is addressed by not using any waterglass and replacing cement with limestone powder.

Firstly, the heat release of binder is studied with an isothermal calorimeter to evaluate the hydration behavior of different types of OPC and the impact of retarders like glucose. Secondly, the CO₂ footprint of WWCB is minimized by (1) reducing the amount of cement and (2) using no additive like waterglass since it is normally applied to establish a good interfacial transition zone between the wood-wool and binder but has a CO₂ footprint of 403 kgCO₂/ton of waterglass (European Commission, 2007). Furthermore, due to the long-time storage of the wood outside (which requires large storage space) the applied wood is more brittle, leading to a reduction on both mechanical and aesthetic performance by having more cruelly wood-wool that often is broken in smaller sizes, hence, lowering the bending strength properties of the board. Therefore, boards are produced with fresh wood-wool and the newly developed binder recipe that is resulted from the hydration behavior analysis.

2 MATERIALS AND METHODS

2.1 Materials

Two types of Ordinary Portland Cement (OPC) are studied in this study, which are commercially available under the brand name CEM I 52.5 R and CEM I 52.5 R white (provided by ENCI, NL) (in this study termed *G* and *W* respectively). The chemical composition of the two cement types determined by X-ray fluorescence (XRF) together with the main cement phases calculated by using the Boque equations are presented in Tab. 1. *G* has a BET surface area of 1.50 m²/g and a mean particle size d_{50} of 14.44 μm while *W* is a bit coarser with a BET surface area of 1.21 m²/g and a mean particle size d_{50} of 16.90 μm. Compared to *G*, *W* has a higher C₃A content (+ 3%) and a higher C₃S content (+ 20%) while with a similar gypsum content (both ± 3%). *W* contains almost no iron to ensure the white appearance. Hence, the content of C₄AF is very small (1%). To study the effect of glucose on the hydration of cement, D-glucose (0.2% of mass of cement) is used in isothermal calorimeter measurements. When glucose is used the variants are indicated with -*g*. Furthermore, the two types of Portland cement are also applied in Clinker form (without the addition of anhydrite that normally is used to bond C₃A). These clinker variants are indicated with a *C*, and termed *W_C* and *G_C*. The hypothesis is that the C₃A, which reacts with the used anhydrite to suppress the reaction of C₃A, will in case of a lower content of anhydrite react partly with the glucose and thereby reduce the initial amount of glucose that could react with the calcium nuclei. Hence, the retardation of the other cement compounds is reduced. The used wood-wool in this study has a width of ±1.5 mm, thickness of ±0.03 mm and length of ±25 cm. Both the bulk and specific densities of the wood-wool are determined by using a Micromeritics AutoPore IV 9500 and is stated to be 761 kg/m³ and 1345 kg/m³ respectively and having a porosity of 63.85%. The target density of the board is aimed to be 450 kg/m³. The wood-wool created from wood logs witch are stored outside for 6 months are termed "old" while the wood-wool witch is immediately after delivery of the logs is created and termed "fresh".

2.2 Measurements

To study the hydration kinetics, tests were performed in a TAM AIR isothermal calorimeter for 90 hours with a water to powder ratio of 0.5 under a temperature of 20 °C. The powder samples were first put in an ampoule and then well mixed before water was added. After the addition of water, mixture was mixed for 2 min. and the ampoule was loaded to the isothermal calorimeter. The heat evolution rate data were calibrated by subtracting the heat evolution of ampoules with water as a baseline.

Tab. 1: Chemical composition and main Boque compounds.


Chemical composition	G	W	Compounds	G	W
CaO	63.71	67.19	C ₃ S	56	80
SiO ₂	20.27	20.86	C ₂ S	17	0
Al ₂ O ₃	4.80	3.91	C ₃ A	7	10
Fe ₂ O ₃	3.43	0.45	C ₄ AF	10	1
SO ₃	2.91	2.92			

In order to investigate if a modified binder would result in an improved WWCB in term of flexural strength, boards were produced with a water to powder ratio by mass of 1.0 and a wood to powder ratio by mass of 0.75 using the following lab scale preparation procedure: First, the wood-wool is pre-wetted, to make the wood-wool more flexible and less vulnerable to break. Secondly, the binder is mixed with water to create a homogenous slurry, which is then applied on the wood-wool by means of spraying. Next, the wood-wool cement composite is transferred into a mold and distributed evenly to form the board. Subsequently, the mold is removed, the composite is sealed and compressed to the desired height, which is achieved by using distant holders of 15 mm. After 24 hours compression, the formed boards are stored for 10 days under ambient conditions. Finally, the boards are dried in an oven at 100 °C for 2 hours to remove the capillary water. During the production of the boards it was found that the fresh wood-wool has a higher moisture content (42.6 % compared to 14.69 % for dry wood-wool), hence, the boards were relatively wet compared to wood-wool stored outside for 90 days and the initial required water was therefore reduced with 20%.

3 RESULTS


3.1 Hydration kinetics OPC and clinker

Fig. 2 illustrates the heat evolution and heat flow rates of *G*, *W*, *G_C* and *W_C* mixtures, in the first 90 h of reaction. Three distinguishable peaks are observed during the recording period as presented in Fig. 2b. A first sharp peak (within the first 10 min.) appears immediately after mixing and is called the pre-induction period, followed by a second broad exothermic peak which is known as the acceleration period and in case of *W* a sharp third peak which also appears in the acceleration period. The first sharp peak is contributed by the dissolution of particles and fast reaction of C_3A that reacts with Ca^{2+} and SO_4^{2-} ions yielding the formation of ettringite (Aft) (Taylor, 1990). This product precipitates on the cement particle surface and eventually together with other reaction products slows down the hydration of C_3S and C_2S . C_3A hydrates in the pre-induction period around 5-25% (Taylor, 1990). The reaction of C_3A with the presence of gypsum and water to form ettringite is written as:



in which: *g* is the hydrogen/ silica ratio in C-S-H.

When all the gypsum in the paste is consumed by the reaction with C_3A , the ettringite starts to further react with C_3A to form monosulfate as:



C_3S reacts in the pre-induction period in small quantities, yielding a C-S-H phase and contributes together with C_2S to the Ca^{2+} and OH^- concentration in the liquid phase. The second peak attributes to the reaction of C_3S and the second stage C-S-H starts to be formed. Because of the formation of calcium hydroxide in the liquid phase, the concentration of Ca^{2+} in the liquid gradually declines. The calcium sulphate becomes completely dissolved and the concentration of SO_4^{2-} ions start to decline, due to the formation of the Aft phase. Finally, a third peak

appears to a second stage reaction of C_3A that reacts with ettringite forming monosulphate (Hewlett, 2004).

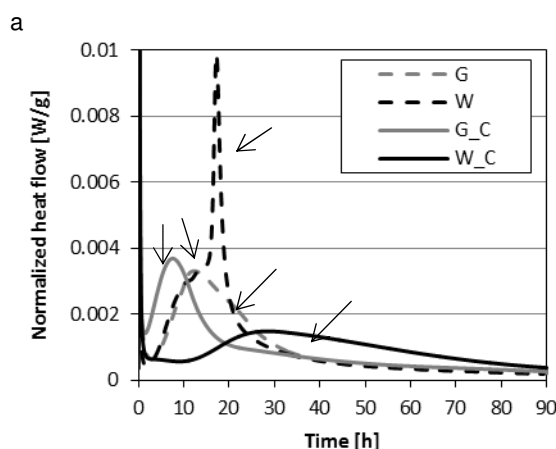
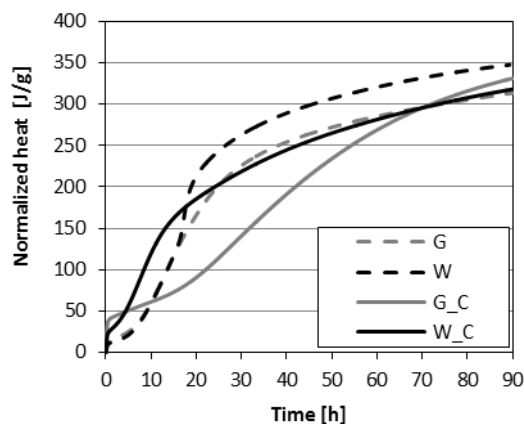



Fig. 2: (a) normalized heat and (b) normalized heat flow of *G*, *W*, *G_C* and *W_C* for 90 hours.

In both the clinker variants (*G_C* and *W_C*) presented in Fig 2, the heat evolution is in the first hour significantly higher compared to the variants without clinker (*G* and *W*), due to a higher dissolution of C_3A forming calcium aluminate hydrate (CAH). Later, this material transforms into hexagonal crystals corresponding to the phases C_2AH_8 and C_4AH_8 . It is expected that the C_2AH_8 and C_4AH_8 are ultimately converted to a more stable hydrate C_3AH_6 . Furthermore, it can be observed that the heat release of *G_C*, after the pre induction period gradually increases (18 h) although a second sharp peak can be observed at 8 h. On the other hand *W_C* shows a heat release rapidly increasing up to 15 h. The function of anhydrite is to slow down the reaction of C_3A , leading to a more gradual reaction of the other phases results into a higher heat release after 90 h compared to a flash set (initial high heat release) in which C_3A reacts and precipitates on the cement particle surface retarding the cement hydration (Taylor, 1990).


3.2 Hydration kinetics OPC, clinker and glucose

The heat evaluation and heat flow rate significantly alter when glucose is added to the mixtures, as presented in Fig. 3. The added glucose initially retards both *W* and *G* until 43 h and 26 h, respectively. The variation in retardation is mainly due to the difference in chemical composition, *G* has a higher content of C_4AF which helps to overcome

the retarding effect of glucose, compared to W which has no C_4AF . Furthermore, the reaction of Aft with C_3A and C_4AF to form AFm is stimulated in case of G and thereby is able to overcome the retarding effect. However, because of the significant amount of C_3S , W rapidly develops heat after it overcomes the retardation of glucose and even exceeds the heat evolution of G at 66 h.

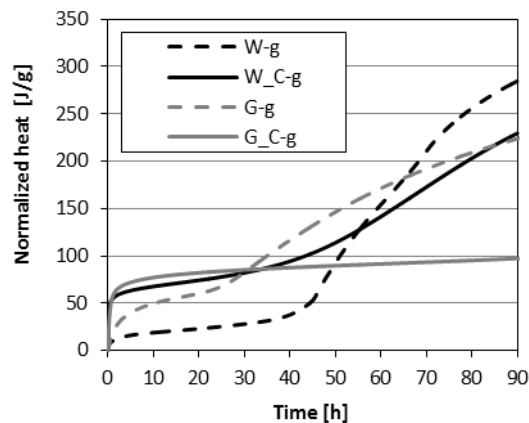

a

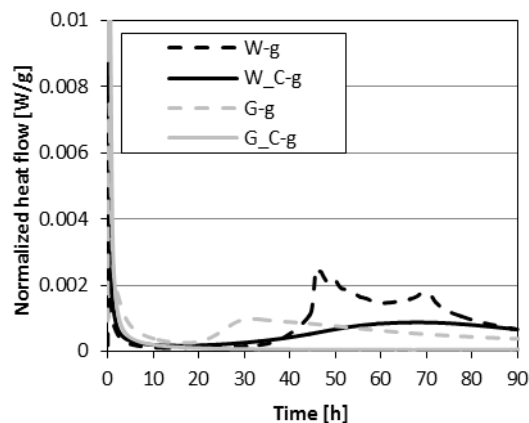

b

Fig. 3: Normalized heat and heat flow of G - g , W - g , G - C - g and W - C - g for 90 hours.

In case of G - C - g and W - C - g it clearly demonstrates that C_3A which now is not bonded with anhydrite bonds with the glucose and increases the early heat evolution of both types to 42 J/g within the first 30 minutes of hydration compared to 24 and 38 J/g for W - C and G - C and 10 and 11 J/g for W and G respectively. Afterwards, less glucose is available to bond other cement compounds. However, in the case of G - C - g , retardation beyond 90 h is observed due to its lower content of C_3S and missing anhydrite. This is in contrast to W - C - g which has a high amount of C_3S that starts to react rapidly after 33 h. Furthermore, it can be observed that due to the fast setting the dissolution and ion-migration at the early age is affected, resulting in a fast set and possible excessive formation of ettringite (Colleparidi et al., 1984).

3.3 Hydration kinetics OPC, clinker, glucose and limestone powder

In order to reduce the CO_2 footprint of the binder, with the requirement to fulfill the stated requirements in EN 13168, the replacement of white cement (W)

by 36% limestone powder (L) is studied (W - L). The remaining cement is replaced by 20% clinker (C) and addition of 0.2% glucose ($-g$) (Fig. 4). Firstly, limestone powder stimulates the reaction of the cement compounds e.g. the heat release of the third peak corresponding to C_3A is increased from 0.01 to 0.21 W/g and acceleration of the hardening can be observed in time (17 h to 13 h) for W - L . Furthermore, it can be seen that when 20% clinker is used as cement replacement (W - L - C), the reaction is further accelerated (13h to 7.5 h) and the heat release peak of the C_3A is even further increased (0.021 to >0.030 W/g). When 0.2% glucose is added (W - L - g) (based on mass of cement) a retarding effect occurs (3 h less than W - g). Furthermore, it is clearly visible that the second C_3A reaction which initially occurs after the C_3S reaction is now shifted and probably changes the structure in terms of porosity of the binder. When 0.2% glucose is added to the 20% clinker variant (W - L - C - g) the early reaction is occurring in a high degree and retardation takes place to a less extent. However, it is also observed that the second C_3A peak disappeared. Within one hour of the reaction the peak is visible indicating that the glucose reacted with the C_3A within the first hour of hydration.

Finally, due to the reaction of glucose with C_3A and reaction with limestone powder the reaction takes place before the reaction of C_3S as the second and third heat release peaks of W - L - g in Fig. 4 are clearly shifted compared to the second and third heat release peak of W - L .

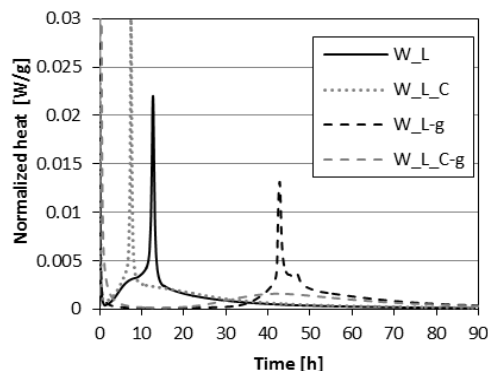
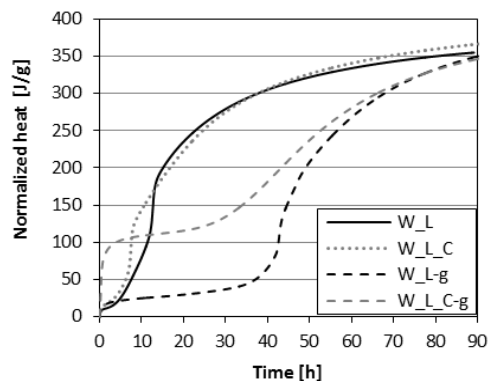


Fig. 4: Normalized heat and heat of white cement (W) replaced by 36% limestone powder (L), 20% clinker (C) and the addition of 0.2% glucose ($-g$) for 90 hours.

Tab. 2: Produced WWCB with their density and flexural strength properties.

* Dried samples with a 20% lower moisture content

Constituent	Fresh [%]	Old [%]
Hemicellulose	21.6	24.4
Cellulose	41.0	38.7
Lignin	33.5	32.7
Extractives	4.0	4.7

Tab. 3: Chemical composition of the used Spruce wood-wool.

Boards	Density [kg/m ³]	Flexural strength [MPa]
100% W (wet)	520.7	5.9
100% W (wet)	550.6	6.5
C_WWCB	455.7	3.0
C_WWCB	538.5	3.9
C_WWCB	570.5	4.9
80% W+ 20% C (wet)	443.3	3.6
80% W+ 20% C (wet)	528.8	7.1
*80% W+ 20% C (wet)	423.8	1.9
*80% W+ 20% C (wet)	451.6	2.9

From the results it can be concluded that the W with high amounts of C₃S and C₃A and 20% less anhydrite can rapidly overcome the influence of glucose and by that it is possible to create boards with sufficient strength within 24 h of hydration.

3.4 Board properties: Flexural strength

Based on the previous results WWCB are produced with the size of 30 x 50 cm² (W x L) and cut into three board of 15 x 20 cm² (W x L). The flexural strength is tested according to EN 12089. Since the distribution of the boards can lead to varying densities, Tab. 2 only presents boards which have comparable densities and a higher density corresponds with a higher flexural strength. The boards termed 100% W are mixed with fresh wood-wool and show extraordinary strength results compared to commercial available WWCB (termed C_WWCB). This was unexpected since it is believed that the wood-wool has a larger amount of inhibitory substances that retard the cement setting and reduce its mechanical performance. Instead the setting of cement seems to be not affected. A reason for this could be a low content of soluble extractives which is a result of the uncertainty of the age of the shredded wood logs in terms of storage time on the forest site. While from the obtained strength results as well as the observed roughness of the wood-wool it is clear that this wood-wool is "more" fresh compared to the old wood-wool these level of freshness is unknown. This later is confirmed by chemical analysis presented in Tab. 3 of the wood-wool which are almost identical. The boards in which fresh wood-wool and clinker was used (termed 80% W+ 20% C (wet)) show strength results exceeding all other boards indicating the positive influence of the clinker by increasing the setting of cement while keeping a similar heat of reaction. The use of old

wood-wool presented lower mechanical strength properties compared to fresh wood-wool. However, when the boards are put in an oven for 24 h at 100 °C, the difference in flexural strength is found to be negligible. Finally, the boards produced with fresh wood-wool, with 36% limestone powder and 20% less water are oven dried and in the range of 450 kg/m³ have a strength >2 MPa and with that are fulfilling the requirements stating in EN 13168. The reduced water amount is based on the high moisture content present in the fresh wood-wool and the reduced cement amount, since limestone powder has a lower water absorption (18% per gram of cement) compared to cement.

4 CONCLUSION

This paper addresses the hydration kinetics of cement with glucose as a strong retarder to find the right cement composition that can overcome this retarder. Furthermore, the newly designed composite is tested by applying fresh wood-wool to produce WWCB Based on the study the following conclusions can be drawn:

- The function of anhydrite is to suppress the reaction of C₃A, leading to a more gradually reaction, resulting into an higher heat release after 90 h compared to a flash set when less anhydrite is used.
- The inhibitory effect of glucose on cement is depending on the chemical composition of the used cement. In case of OPC (with anhydrite), both C₃A and C₄AF form ettringite and will not affect the hydration of the calcium silicate phases and will in a low degree retarded by glucose. In case of OPC which does not contain C₄AF and instead has a higher C₃S content will be strongly retarded by glucose, although in a later stage can rapidly release heat.
- In case clinker (no anhydrite present) coverage of the cement phases C₃S and C₂S is observed due to the reaction of C₃A and C₄AF reducing the rate of hydration. In case of clinker with a high content of C₃S and low content of C₄AF this phenomena does not occur.
- In combination with glucose and clinker. Glucose bonds C₃A, increasing the heat release and reducing the retarding effect. In case less C₃A is present, a higher percentage of glucose can react with the remaining phases. Furthermore, the retarding effect, because of the C₃A and C₄AF and lower amount of C₃S is increased significantly.

Regarding the produced boards and there flexural strength, it can be concluded that:

- The fresh wood-wool which initially was used to evaluate the retarding effect on the binders does not show a significant impact on the binder.
- Fresh wood-wool compared to Old wood-wool show a higher roughness, making it less brittle and remaining its length leading to higher flexural strength.
- The produced boards show comparable or higher strength results compared to commercially available WWCB.
- The use of limestone powder as a partial cement replacer to produce boards in the range of range

of 450 kg/m³ have a strength >2 MPa and with that are fulfilling the requirements stating in EN 13168.

5 FURTHER RESEARCH

Further research will be conducted on the initial moisture and extractive content of wood logs in order to validate performance of replacing cement with 20% clinker and the use of 36% limestone powder without the use of additives. Furthermore, a study will be performed to select wood logs based on their moisture content, to see if the mechanical performance of the wood-wool can be linked with the initial moisture content of the wood logs.

6 ACKNOWLEDGMENTS

The authors would like to acknowledge STW-foundation, Dr. Jan van Dam (Wageningen UR), Knauf Insulation, ENCI B.V., and Eltomation for their provision of material, technology and financial support.

7 REFERENCES

Aro, M., 2004. Wood strand cement board. In *11th Int. Inorganic-Bonded Fiber Composites Conference*. Madrid-Spain, pp. 169–179.

Ashori, A. et al., 2011. Wood–wool cement board using mixture of eucalypt and poplar. *Industrial Crops and Products*, 34(1), pp.1146–1149.

Colleparidi, M. et al., 1984. Influence of gluconate, lignosulfonate or glucose on the C3A hydration in the presence of gypsum with or without lime. In *Cement and Concrete Research*. pp. 105–112.

Commission, E., 2007. Integrated Pollution Prevention and Control, Reference document on

best available techniques for the manufacture of large volume inorganic chemicals - solids and other industry. , I(August).

Fan, M. et al., 2012. Cement-bonded composites made from tropical woods: Compatibility of wood and cement. *Construction and Building Materials*, 36, pp.135–140.

Hachmi, M. et al., 1990. A new technique to classify the compatibility of wood with cement *. *Wood Science and Technology*, 354(608), pp.345–354.

Hachmi, M. & Moslemi, A.A., 1990. Effect of Wood pH and Buffering Capacity on Wood-Cement Compatibility. *Holzforschung*, 44(6), pp.425–430.

Hewlett, P.C., 2004. *Lea ' s Chemistry of Cement and Concrete*,

Karade, S.R., 2010. Cement-bonded composites from lignocellulosic wastes. *Construction and Building Materials*, 24(8), pp.1323–1330..

N.L. Thomas, J.D.B., 1983. The retarding action of sugars on cement hydration. *Cement and Concrete Research*, 13(c), pp.830–842.

Neville, A.M., 2002. *Properties of concrete*

Pereira, C. et al., 2006. Characterizing the setting of cement when mixed with cork, blue gum, or maritime pine, grown in Portugal I: temperature profiles and compatibility indices. *Journal of Wood Science*, 52(4), pp.311–317.

Poletto, M., Zattera, A.J. & Santana, R.M.C., 2012. Thermal decomposition of wood: Kinetics and degradation mechanisms. *Bioresource technology*, 126C, pp.7–12.

Simatupang, M.H. & Geimer, R.L., 1990. Inorganic binder for wood composites: feasibility and limitations. In *Wood Adhesives*. Madison, Wisconsin, USA, pp. 169–176.

Taylor, H.F.W., 1990. *Cement chemistry*